

Observation of microstructures of atmospheric ice using a new replica technique

ML.A. Pervier^a, H. Pervier^a, D.W. Hammond^a

^a Cranfield University, Cranfield, MK43 0AL, UK

Abstract

A replication technique has been developed to study the microstructure of atmospheric ice based on the use of nail varnish rather than more harmful materials. The potential of the technique was demonstrated by obtaining and reporting microstructures for impact ice grown on metal surfaces in an icing tunnel under a range of cloud conditions. The technique reveals grain structure, growth striations, porosity and etch features which may indicate an aspect of crystallographic orientations.

Keywords:

atmospheric ice, impact ice, microstructure, grain size

In order to study the mechanical response of atmospheric ice including adhesion to a substrate, knowledge of the ice's microstructure is of prime importance. Atmospheric ice by its nature is very different from other types of ice and varies significantly in its microstructure. Impact ice is formed by the freezing of super-cooled droplets when they strike a surface. Lake ice, sea ice or other types of ice grown by cooling a body of water are dominated by the fact that the cooling is limited by thermal conduction effects. This generally results in producing much coarser grain size, modifying grain aspect ratio and influencing pore size and distribution compared to impact ice.

1. Previous work

While knowledge of the microstructure of ice is important for understanding the fracture process and ice adhesion, as it is in many structural materials, only a small number of authors have reported such data. This is perhaps due to the difficulty of handling a material which is easily broken and modified by a slight change of temperature.

Different methods to observe ice microstructure have been reported by Blackford (2007). Depending on the methods used, different level of details can be studied and they all present their advantages and drawbacks. The most direct method, and most commonly used, is

to make and observe a thin slice of ice under a microscope using reflecting or transmitted light. With a resolution of $1\text{ }\mu\text{m}$, this method allow the observation of the size, shape and distribution of the grains as well as the location and distribution of the impurities. The use of polarized light gives more information on the crystallographic orientation of each grains (Durand, 2006). The main drawbacks of the methods resides in the preparation of thin sections of ice and in avoiding any transformation of the ice microstructure with time.

To overcome the difficulties of handling and keeping the sample intact, several authors (Nasello et al., 1987; List et al., 1970; Higuchi, 1958; Fortin and Perron, 2009) have used a replication technique based on a solution of formvar dissolved in a solvent such a chloroform. This is known to be toxic and carcinogenic (Takahashi and Fukuta, 1987). Other authors (Takahashi and Fukuta, 1987; Kriston et al., 2016) have used an alternative to formvar. Takahashi and Fukuta have successfully replicate ice crystal using common plastics dissolved in solvent and discussed the ability of each combination. Best results were obtained using plexiglas with ethylene dichloride or trichloroethylene and polystyrene with 1,1,1-trichloroethane or carbon tetrachloride. While these solvents have the advantage of remaining clear, compared to formvar, due to the absence of water soluble ingredients, they are still harmful. Kriston et al. reported work on the effect of the friction of rubber tyre on ice. They replicated the ice surface by using a dental casting material called vinyl polysiloxane. They obtained a negative replica of the

URL: m.pervier@cranfield.ac.uk (ML.A. Pervier),
d.w.hammond@cranfield.ac.uk (D.W. Hammond)

ice surface which was then used as a mould to obtain a positive replica using polyurethane. Depending on the level of detail required, optical microscope, SEM or white light interferometer was used. Grain and sub-grain boundaries, etch pits, frost and scratches due to the effect of multiple sweeping of rubber on ice were observed.

In the present paper, a similar technique has been tested but by replacing the solution of formvar with less harmful nail varnish. While nail varnish composition generally includes some kind of alcohol and acetone, the proportion of these in some nail varnish is low enough to not cause any damage to the ice surface. A description of the method and the level of detail that can be obtained is presented in the following.

2. Methodology

Samples of ice were produced in Cranfield Icing Tunnel (Hammond, 2003) as a by product of mechanical tests. Ice was accreted on the front face of cylinders made of either Titanium alloy Ti-6Al-4V or Aluminium alloy Al2024-T3 (figure 1). The substrate surfaces were

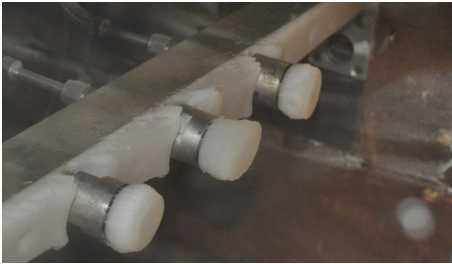


Figure 1: Samples of ice accreted on the front face of metallic cylinders ($T=-15^{\circ}\text{C}$, $V=80\text{ m.s}^{-1}$, $\text{LWC}=0.3\text{ g.m}^{-3}$, $\text{MVD}=20\text{ }\mu\text{m}$)

polished to mirror finish with a resulting roughness of $0.3\text{ }\mu\text{m}$ (Ra). The pieces of ice were detached from the metallic surface using a hammer and a chisel and positioned at the bottom of a chest freezer straight after removal. The removal was completely adhesive meaning that the substrate surface was visually free of ice. The ice pieces were kept in loose fitting plastic bags in the freezer at a temperature of -18°C for a couple of weeks before the surface were replicated using the nail varnish technique. During this resting time, sublimation will have occurred revealing the grain boundaries as this process is faster along the grain boundaries than within the body of the grain. A layer of nail varnish was applied to the surface of interest using the small brush provided with the nail varnish bottle. After a drying time of 14 to 20 hours, the nail varnish layer was

peeled off the ice giving the replica including imprint of the peaks and groves present on the ice surface. Three different types of replica were collected representing different orientations and regions of each ice specimen. These are shown in figure 2.

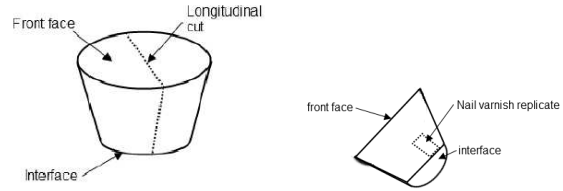


Figure 2: surface replica of the ice sample

The three types of replicas collected are referred as follows:

- the surface which was in contact with the substrate (called the interface)
- the surface at the other extremity (called the front surface)
- a longitudinal surface which was obtained by cutting the ice piece normal to the substrate surface

In most of the samples, the interface and the front surface were both replicated directly without the need to prepare the sample further. When the surface was not flat enough (it is mostly the case with the front surface of glaze ice), the ice surface was manually polished using carbide paper. As this process leaves some groves onto the surface, the ice piece needed to be left in the freezer for a further week to allow the sublimation process to remove them. The longitudinal surface was cut in a cooled environment (-15 to -20°C) using a saw with relatively large teeth to help the sawing action. The saw was also cooled prior to any sample cutting. One of the two halves was chosen and further ground with fine grain metalurgical grade silicon carbide paper (180 grit). The sample was then left to sublimate for several days in the freezer. The nail varnish was applied using from the interface side to the front surface (figure 2). Replicas were prepared for the microscopic observation by sandwiching them between a microscope slide and a cover slip. They were observed under transmitted unpolarised light in a microscope and photos taken. The photos were stitched together using the software iMerge¹. The average grain size was obtained, for each case, by

¹iMerge is an images stacking and mosaic-making software conceived primarily for astronomical purpose

using the mean linear intercept method on ten separate measurements (standard deviation of 10%).

3. Description of the microstructure obtained

The images collected allow us to see the grain boundaries of the ice sample as well as the presence of air pockets. In some cases, when the grains dimensions are large, some thermal etch pits becomes visible.

3.1. Different surfaces of the same piece of ice

Figure 3 to 5 present the three different surfaces of interest of the same piece of ice as described above. The ice was produced at a relatively high ambient tunnel temperature (-5°C), a moderate tunnel wind speed (50 m.s^{-1}) and relatively low LWC (0.3 g.m^{-3}). The resulting ice had a transparent aspect but was not completely glazed. The deposit temperature, measured with a thermocouple placed inside the metallic cylinder (on which the ice was accreted on) close to the surface, was slightly below the melting point of ice at -1°C . The freezing fraction (fraction of the liquid water that becomes ice on impingement) was estimated around 0.5.

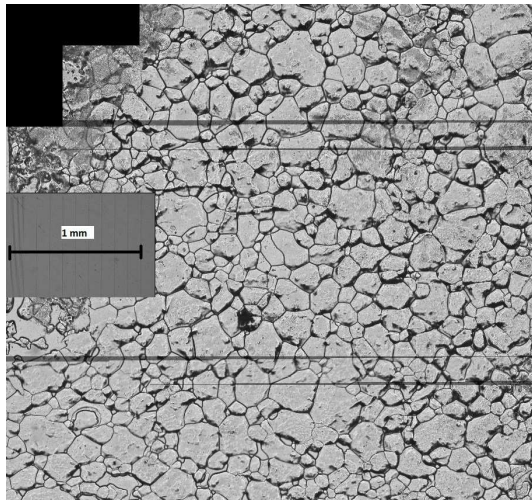


Figure 3: Microstructure of the interface of ice built on a mirror polished surface finish titanium alloy substrate ($T=-5^{\circ}\text{C}$, $\text{LWC}=0.3 \text{ g.m}^{-3}$, $V=50 \text{ m.s}^{-1}$, $\text{MVD}=20 \mu\text{m}$)

Figure 3 shows the aspect of the grain at the interface ice/substrate. The polycrystalline structure of this type of ice was clearly visible. The average size of the grains was $155 \mu\text{m}$ in the plane of the section. The straight horizontal lines and the fading of light in some part of the picture is an artefact effect due to the mosaic composition of the photos. The microstructure of the far side of

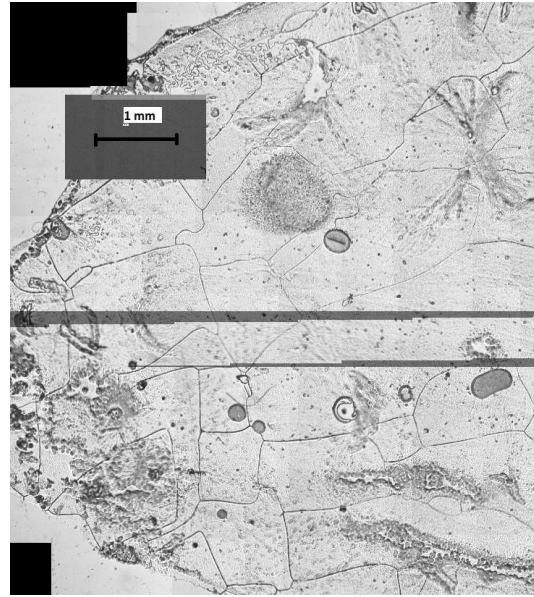


Figure 4: Microstructure of the front face of ice built on a mirror polished surface finish titanium alloy substrate ($T=-5^{\circ}\text{C}$, $\text{LWC}=0.3 \text{ g.m}^{-3}$, $V=50 \text{ m.s}^{-1}$, $\text{MVD}=20 \mu\text{m}$)

the ice block, the front side, can be observed in figure 4. Even if the scale is slightly different, it can immediately be seen that the grains are much larger than at the interface. The average size of the grains was $1094 \mu\text{m}$. A few round big bubbles can be spotted. These are water bubbles that have been trapped when the ice replica was sandwiched between the microscope slide and the cover slip for the observation under the microscope. More details of the evolution of the grain structure can be observed in figure 5. This figure represents the microstructure on a longitudinal cut through the ice piece. The part closer to the interface is on the bottom side of the picture while the front face is on the top side. The grains can be seen to have a columnar structure. They are much narrower at the interface and gradually became wider near the front face. The black spots are the results of crystallisation of the nail varnish replica and are an artefact obtained when the nail varnish is left for too long on the ice sample during the replication process.

3.2. Air bubbles

Another feature that can be observed using the nail varnish replica method is the presence and the size of air pockets within the ice. These air pockets can be of different kind and differ mainly by the way they are formed. One of the kind is due to air contained in

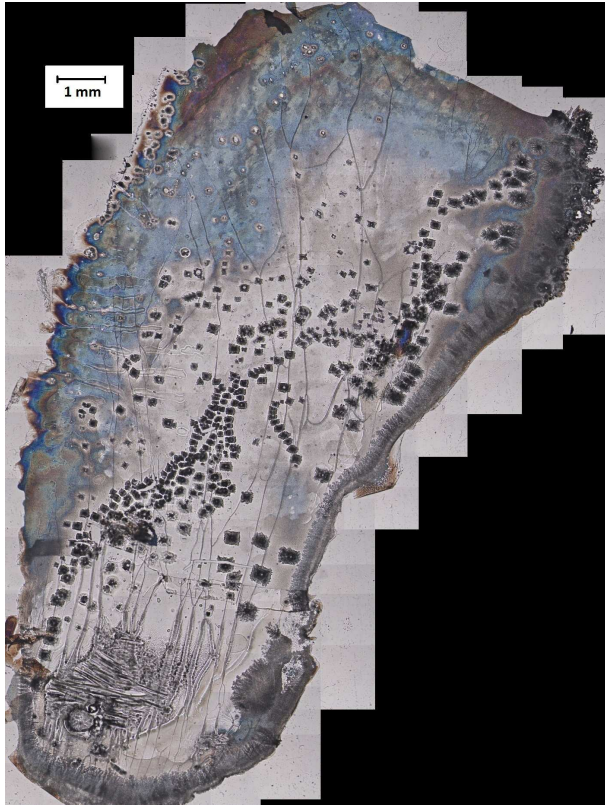


Figure 5: Microstructure of the longitudinal cut of ice built on a mirror polished surface finish titanium alloy substrate ($T=-5^{\circ}\text{C}$, $\text{LWC}=0.3 \text{ g.m}^{-3}$, $V=50 \text{ m.s}^{-1}$, $\text{MVD}=20 \mu\text{m}$)

the water droplets which is dissolved during the ice accretion and remained trapped within the ice (Eskandarian and Farzaneh, 2005; Macklin, 1962). Another kind which happens mainly with rime ice at low LWC, is formed when the water droplets impinge the surface and dry patches are created between each droplet.

Tiny air bubbles can be seen on figure 6 as small black dots especially present along the grain boundaries. This picture represents the interface part of an ice sample grown on mirror polished aluminium alloy at a tunnel total temperature of -20°C , a speed of 50 m.s^{-1} , a LWC of 0.3 g.m^{-3} and a droplet mean volume diameter of $20 \mu\text{m}$. These icing conditions resulted in an ice sample which had a white appearance and a freezing fraction of 1. This means that each droplets coming into contact with the metallic surface would freeze completely when impinging the surface. This type of ice is commonly referred as rime ice. On this particular example, the average size of the grains was $52 \mu\text{m}$ and the size of the air bubbles was around $10 \mu\text{m}$.

Another type of bubbles, more accurately referred

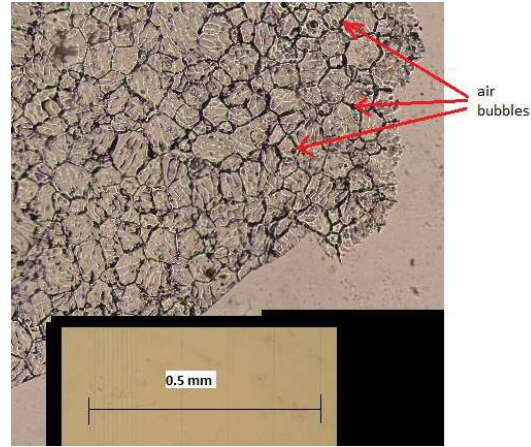


Figure 6: Microstructure of the interface of ice built on a mirror polished surface finish aluminium alloy substrate ($T=-20^{\circ}\text{C}$, $\text{LWC}=0.3 \text{ g.m}^{-3}$, $V=50 \text{ m.s}^{-1}$, $\text{MVD}=20 \mu\text{m}$)

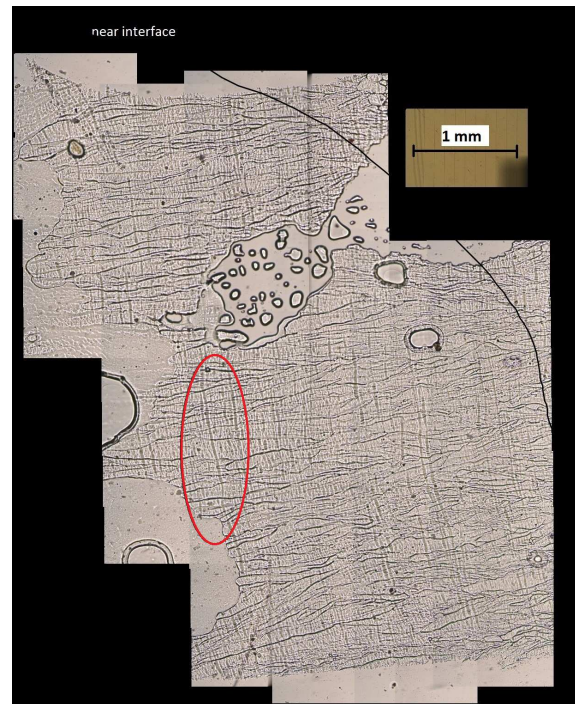


Figure 7: Microstructure of the longitudinal cut of ice built on a mirror polished surface finish titanium alloy substrate ($T=-15^{\circ}\text{C}$, $\text{LWC}=0.3 \text{ g.m}^{-3}$, $V=80 \text{ m.s}^{-1}$, $\text{MVD}=20 \mu\text{m}$)

as porosity and described previously by Laforte et al. (1983), can be spotted on figure 7 (an example of them has been circled in black on the figure). This picture represents the microstructure of a longitudinal cut of a sample of ice grown on mirror polished titanium alloy at a temperature of -15°C . The grains here were columnar

and relatively elongated in respect to their width (aspect ratio of around 20). A few of the black round dots described before can be spotted but more interestingly, some faint wavy vertical lines can be observed almost perpendicular to the grain boundaries. These are made of tiny bubbles and represent variations in fine porosity. They also allow us to visualise the advancement of the growth of the ice front.

3.3. Thermal etch pits

The last feature described in this paper have been previously reported by Nasello et al. (1987) and Kriston et al. (2016). It was only observed when the size of the grains were reasonably wide (above $100\text{ }\mu\text{m}$).

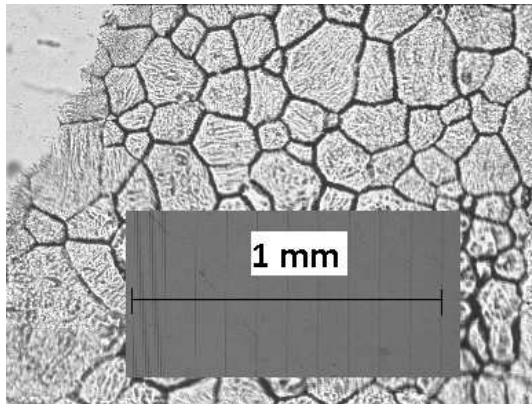


Figure 8: Microstructure of the interface of ice built on a mirror polished surface finish aluminium alloy substrate ($T=-10^{\circ}\text{C}$, $\text{LWC}=0.8\text{ g.m}^{-3}$, $V=50\text{ m.s}^{-1}$, $\text{MVD}=20\text{ }\mu\text{m}$)

On figure 8, faded greyish non continuous small lines can be spotted inside most of the grains. These are thought to be arrays of thermal etch pits and can give some indication of the orientation of the crystal c-axis.

4. Conclusion

It has been demonstrated that nail varnish may be used to observe the microstructure of atmospheric ice. This method reduced considerably the preparation of the sample compared to more conventional method used previously to observe the microstructure of ice. Furthermore the ice replicas are not destroyed by time as would a thin slice of ice and can be observed as many times as needed.

These replicas allow the observation of many features as the size and shape of the grains, the presence of air inclusions, the growth lines of ice and the thermal etch pits that give an indication of the orientation of the c-axis.

The technique offers a relatively simple way to observe ice microstructures so that it may be possible for more research on ice feature to be supported with reporting ice microstructural information.

5. Acknowledgement

The research leading to these results has received funding from the European Union seventh framework programme (FP7/2007-2013) under Grant Agreement no.605180.

References

- Blackford J.R. (2007) Sintering and microstructure of ice: a review. *Journal of physics D: applied physics* vol.40 R355-385
- Durand G., Gagliardini O., Thorsteinsson T., Svensson A., Kipfstuhl S., Dahl-Jensen D. (2006) Ice microstructure and fabric: an up-to-date approach for measuring textures. *Journal of glaciology* vol.52 no.179 pp.619-630
- Eskandarian M., Farzaneh M. (2005) Texture and fabric characteristics of atmospheric ice deposits on overhead power lines. *IWAIS XI*
- Fortin G., Perron J. (2009) Spinning rotor blade tests in icing wind tunnel. *AIAA* 2009-4260
- Hammond D., Luxford G., Ivey P. (2003) The Cranfield University Icing Tunnel. *AIAA* 2003-0901
- Higuchi K. (1958) The etching of ice crystals. *Acta Metallurgica* vol.6
- Kriston A., Isitman N.A., Fülöp T., Tuononen A.J. (2016) Structural evolution and wear of ice surface during rubber-ice contact. *Tribology international* vol.93 pp.257-2688
- Laforte J.L., Phan L.C., Felin B. (1983) Microstructure of ice accretions grown on aluminium conductors. *Journal of climate and applied meteorology* vol.22 no.7, pp.1175-1189
- List R., Cantin J.G., Ferland M.G. (1970) Structural properties of two hailstones samples. *Journal of atmospheric sciences* vol.27 pp.1080-1090
- Macklin W.C. (1962) The density and structure of ice formed by accretion. *Quarterly Journal of the Royal Meteorological Society* vol.88 no.375 pp.30-50
- Nasello O.B., Levi L., Prodi F. (1987) Crystal structure of ice accreted on an ice substrate. *Journal of glaciology* vol.33 no.113
- Takahashi and Fukuta (1987) Ice crystal replication with common plastic solutions. *Journal of atmospheric and oceanic technology* vol.5 pp.129-135

Observation of microstructures of atmospheric ice using a new replica technique

Pervier, Marie-Laure

2017-05-13

Attribution-NonCommercial-NoDerivatives 4.0 International

Pervier MA, Pervier H, Hammond DW. (2017) Observation of microstructures of atmospheric ice using a new replica technique. Cold Regions Science and Technology, Volume 140, August 2017, pp. 54-57

<http://dx.doi.org/10.1016/j.coldregions.2017.05.002>

Downloaded from CERES Research Repository, Cranfield University