

# IMPACT OF DUST ON ELECTRICAL POWER OUTPUT OF SOLAR PV MODULES IN NORTH-EAST, NIGERIA

<sup>1</sup>Hauwa Talatu Abdulkarim; <sup>2</sup>Chris Sansom; <sup>3</sup>Kumar Patchigolla;  
<sup>4</sup>Heather Almond & <sup>5</sup>Mounia Karim

**Corresponding E-mail:** talatuabdulk@gmail.com; c.l.sansom@cranfield.ac.uk;  
k.patchigolla@cranfield.ac.uk; m.karim@cranfield.ac.uk & h.j.a.almond@cranfield.ac.uk

<sup>1</sup>Department of Electrical/Electronic Technology, College of Education, Minna

<sup>2</sup>Concentrated Solar Power, Centre for Energy and Power, Cranfield University, Cranfield, MK43 0AL, United Kingdom

<sup>3</sup>School of Water, Energy and Environment, Cranfield University, Cranfield, MK43 0AL, United Kingdom

<sup>4</sup>Concentrated Solar Power, Centre for Energy and Power, School of Water, Energy and Environment, Cranfield University, Cranfield, MK43 0AL, United Kingdom

<sup>5</sup>Centre for Renewable Energy Systems, Centre for Energy and Power, School of Water, Energy and Environment, Cranfield University, Cranfield, MK43 0AL, United Kingdom

---

## Abstract

The impact of dust on the solar PV modules deserves more attention. North-eastern Nigeria has high potential of solar irradiance but it is prone to dust accumulation. This paper therefore, investigated the impact of dust on the performance of solar Photovoltaic modules in North- Eastern Nigeria. The investigation entailed field experiment carried out in Maiduguri to assess the performance of the module based on continuous dust deposition for 14 days during dust accumulation period. The results show that more than 50% loss in power output was recorded under 14 days of continuous deposition. The efficiency of the module reduced from 17.1% on the first day to 7.2% on the fourteenth day of the experimentation. The investigation also shows that at high humidity the PV performance drops. Solar irradiance increases the performance. The deployment of solar PV energy supply system is recommended in spite of dust accumulation challenges. To maintain adequate performance of the system, a once-a-week cleaning is recommended during intense dust accumulation period.

**Keywords—Dust, efficiency, modules performance, photovoltaic, solar.**

---

## 1.0 Introduction

The performance of solar PV module is greatly affected by dust which is an emerging area of research in photovoltaic energy conversion system. The studies conducted by (Menoufi, 2017), stated that only 72 studies were conducted on the impact of dust on the


performance of solar PV panels globally. The study presented Africa to have contributed only 12% which amounts to about 8.64 approximately 9 studies in 26 years. This is grossly inadequate considering that Africa is one of the worst dust accumulation zones in the world, in addition to the fact that there are many initiatives that support renewable energy cooperation between Europe and Africa (Menoufi, 2017; Mann, 2012; Menoufi et al., 2017). This further confirms that there are scanty literatures on the effect of dust on the performance of PV panels and therefore, buttresses the need for the study on the effect of dust in Maiduguri, Nigeria. This is a region endowed with solar energy potential, good enough for solar photovoltaic energy supply deployment but unfortunately characterized by intense dust accumulation events compared to other part of the country. Solar energy is a renewable energy of choice but the intermittent nature of the solar resource at any location makes solar data analysis imperative and an important prerequisite to accurate sizing of solar PV system components. Nigeria, a country endowed with solar energy and has grossly insufficient energy supply to its citizens for both domestic and industrial purposes, requires a low-cost solar energy conversion system for the development of local communities.

Solar energy has the capacity, if efficiently harnessed, to supply sufficient energy to rural areas in Nigeria, which are far from the National grid. Also, the development of solar PV technology is a modern energy system which unlocks access to improved healthcare, improved education, improved economic opportunities and, even, longer life, for those who go solar. Nigeria has the highest population in Africa (Kamer, 2022). Unfortunately, Nigeria is among the countries with the lowest electricity consumption per capita in the continent (74 kWh/year) (Ibitoye and Adenikinju, 2007). The residential electricity use per capital of Nigeria is very low and this has contributed tremendously to the poverty level of the citizenry (Ibitoye and Adenikinju, 2007). Also, because the region under study is a region where dust is prevalent and apart from the fact that there is scanty literature on effect of dust, the researches have varying results from region to region combine also with the fact that no such study has been carried out in this region. All these necessitated the study of the effect of dust on PV panels in North-eastern, Nigeria.

Maiduguri in the North-eastern Nigeria is the most dust accumulation region in the country and the most suitable region for the development of solar energy conversion system and with larger rural communities without access to electricity. This makes the development of solar energy conversion system in this region very important and the study of the impact of dust imperative to guide the maintenance and cleaning of the modules for optimum power supply. The experiment to investigate the impact of dust on the performance of PV modules was conducted in Maiduguri, North-eastern Nigeria during the most dust event period. This occurs annually between the month November and March.

## 2.0 Materials And Methods

The material used in the research include electrical measuring instrument such as Mooshimeter with the capability to measure current and voltage concurrently and log the results, solar radiation meter, anemometer, hygrometer, and a 50 W solar photovoltaic module. The 50 W monocrystalline solar PV module (TDG-PV Model T050M365), the data of which is presented in Table I was used for the experiment. The experimental was set-up as shown in Figure 1. The current and voltage were measured at an interval of 10 minutes using Mooshimeter, an instrument that can measure current and voltage concurrently and data logged. The Mooshimeter was set to log the readings every 10 minutes for 14 days during the day.

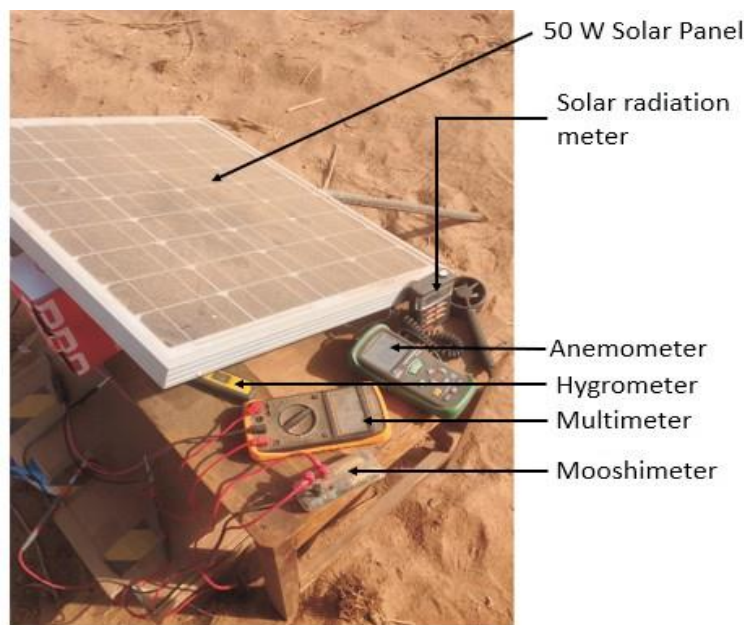

**Figure 1: Experimental Set-up for effect of dust on PV performance**

The ambient temperature, humidity, solar irradiance, and wind speed were recorded every hour. The experiment was conducted from 06:00 to 18:00 hours daily for 14 days. Figure 1 shows the experimental set-up for the study of impact of dust on the performance of PV module.

**TABLE 1: KEY SPECIFICATIONS OF TDG-PV T050M365**

S/N	PARAMETERS	SYMBOL	VALUE
1	Rated maximum power	$P_{max}$	50W
2	Voltage at maximum power	$V_{mp}$	18.75V
3	Current at maximum power	$I_{mp}$	2.690A
4	Open-circuit voltage	$V_{oc}$	22.83V
5	Short-circuit current	$I_{sc}$	2.940A
6	Operating temperature	$T_c$	-40oC to +85oC
7	Cell Technology	Mono-Si	
8	Weight	$W_c$	4.0 kg

## Data from the Name Plate of the 50 W solar panel used for the experiments

### 2.1 Dust Collection and Analysis

The accurate quantification of power decline over time that the solar panels experience is referred to as degradation, which must be known in order to predict power delivery. And the ability to accurately predict power delivery over the course of time is of vital importance to the growth of PV industry. In order to assess the potential deterioration of the Photovoltaic modules which could eventually lead to panel degradation, it is important to have full knowledge of how the deterioration by sand occurs. It is from high wind speed to high wind storm to high sand/dust transportation that leads to potential deterioration.

In this study, we intend to determine the properties of the sand/dust that could reach the module surfaces. Therefore, during the Maiduguri field experiments on the impact of dust, the dusts were collected at different heights. Four wooden poles with fixed collector plates were individually planted at different positions and at the heights of 0.5 m, 1.0 m, 1.5 m and 2.0 m for dust collection for a period of 14 days. This collection was done outside Maiduguri town. The collected dust samples were placed in different containers properly labelled. The analysis of these samples was carried out in Cranfield University, United Kingdom. Figure 2 shows the wooden poles and the plastic plates for dust collection at different heights.

Dust naturally falls into the plastic plates, the dust from each plastic plate was put in a polythene bag and taken to Cranfield for analysis. Dust does not require any preservation in this regard.

In addition, and for comparison, sand was collected from the ground level as well as from the module surface. Dust collected at different heights in order to compare and note the possible kind of particles that could reach the panels' surfaces since collection at different heights will have different results of the characterization. The characterization of the particles will have effect because dust particle sizes varies with height of collection. At higher height, particle sizes are finer and have less damaging impact on the glass of the solar panel. At lower heights, the particle sizes are bigger and can cause cracks either visible or invisible cracks on the panel, which obviously affects the output of the solar panel.



**Figure 2: Wooden poles and plastic plates for dust collection**

## **2.2 Characterisation Technique**

After collecting the sand from the site, a set of analyses were carried out at Cranfield University laboratories in order to determine the main characteristics of the sand/dust particles present in the site. Three phases of analysis were conducted as enumerated below:

- High precision digital weight balance was used to determine the initial mass of sand collected from each height; the objective is to see how much particles are collected according to the height.
- Another analysis that was carried out before the phase separation is particle size distribution.
- The mass of the samples was weighted by high precision digital weigh balance. The particle size distribution of the aggregate collected were analysed using Mastersizer 3000. Wet separation of fraction of sand/soil was carried out. The chemical compositions of the samples were determined using X-ray diffraction.

**The analysis conducted are particle size distribution, soil sand fraction, sand particle shape and nature and chemical analysis of the sample. Details are presented in the next section.**

### **2.2.1 Particle size distribution**

Sample of sand was properly mixed with the aid of spatula and small quantity was taken and poured into the wet sample dispersion unit (i.e a unique dip-in centrifugal pump and stirrer that achieves full and rapid dispersion in a standard laboratory beaker) of the Mastersizer 3000 for analysis. The distribution was made into seven groups viz; 0 - 50  $\mu\text{m}$ ,

50 - 100  $\mu\text{m}$ , 100 - 150  $\mu\text{m}$ , 150 - 250  $\mu\text{m}$ , 250 - 500  $\mu\text{m}$ , 500 - 1000  $\mu\text{m}$  and >1000  $\mu\text{m}$ .

### 2.2.2 Sand and soil separation

After weighing each of the samples from the four different heights of collection, sand and soil separation was carried out using phase separation method. This entails putting samples in a clean bottle and pouring distilled water to allow dirt to float and was removed. This was done a couple of time until it became clean of dirt. A fresh distilled water was then poured into the bottle containing the sample and shaken lightly to allow smooth soil particle to float in the water.

The suspension mixture was poured out of the bottle leaving sand particles settled below the bottle. The bottles were then labelled with their contents as either sand or soil. This procedure was repeated for all the individual samples collected from the four different heights. The bottles were placed in an oven set to 150°C to dry the sand and soil. The dried samples were then taken to analyze the characteristics of the collected particles (i.e. size, morphology and mineralogy) using scanning electron microscope and Energy Dispersive X-Ray Spectroscopy (SEM-EDX).

## 3. 0 Results and Discussion

Figure 3 shows the time series plot of peak power output of the 50 W module for the 14 days of the experiment. Because the output power depends on the irradiance at any time, the time series plot shows rise in power from morning hours and reaching maximum during the afternoon of each day. The effect of dust accumulation over the 14 days of the field work can be seen in the reduction in power output by the day as shown in Figure 3. Day 1 recorded the maximum power output of about 50 W at 2:00 pm and day 14 recorded the lowest power output of about 20.5 W. This is an indication that the maximum irradiance occurred at 2:00 pm. There was over 50% drop in power output during the period of the field work. This agrees with over 50% reduction in power as a result of dust accumulation on PV modules in Egypt presented by (Menoufi, 2017).

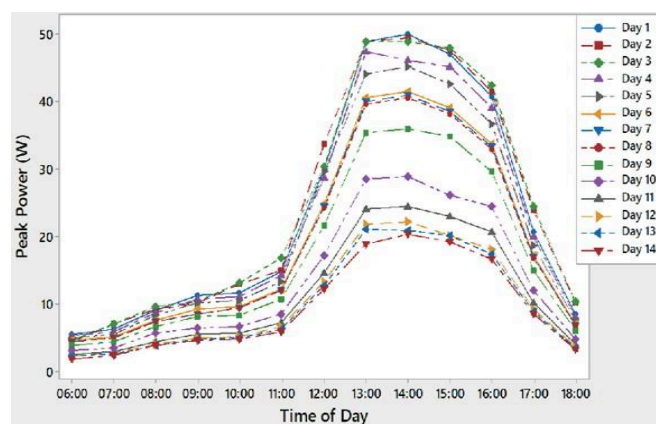



Figure 3: Time series plot of Peak Power for 14 Days

The reduction in the efficiency as a result of drop in performance owing to dust




accumulation was studied over the 14 days of the field work. Figure 4 shows the time series plot of peak power and efficiency during the 14 days. The highest efficiency of 17.1% was obtained on the first day and the least efficiency of 7.2% was obtained on the last day amounting to a 57.6% drop in efficiency.

This drop in performance was because of continuous deposition of dust on the solar module without cleaning for 14 days which is the basis for the study. This implies that during peak dust period in Maiduguri, there is high loss in performance in just two weeks, it is therefore necessary to clean solar modules at least once in every week to be able to maintain reasonable reduction in inefficiency.

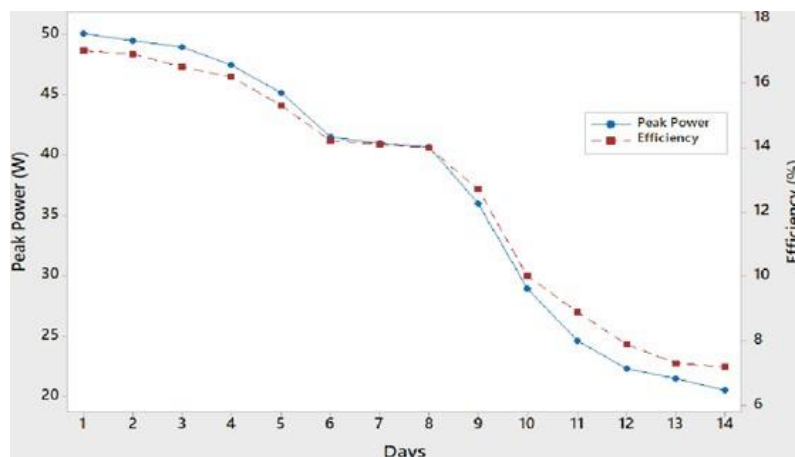


**Figure 4: Peak Power and Panel Efficiency against Days**


Figure 5 to Figure 7 shows the fitted regression line plots of the relationship between peak power output of the 50 W solar PV module and solar irradiance. The regression line shows a positive correlation with coefficient of determination, R<sup>2</sup> being 97.5% 96.8% and 99.4% for days 1, 5 and 8 respectively. This indicates that increase in solar irradiance directly translates to increase in power output of solar photovoltaic modules. This is supported by a number of literatures (Nasiriet al., 2019; Karafil et al., 2016; Chanchangi et al., 2020).

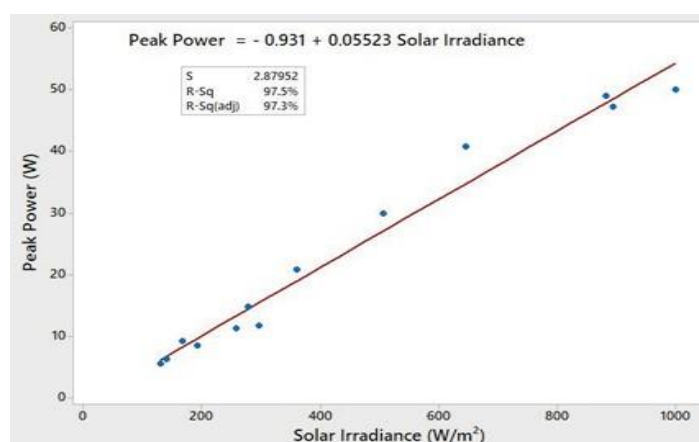

**Figure 5: Fitted regression line plot for Peak power versus Solar Irradiance (Day 1)**

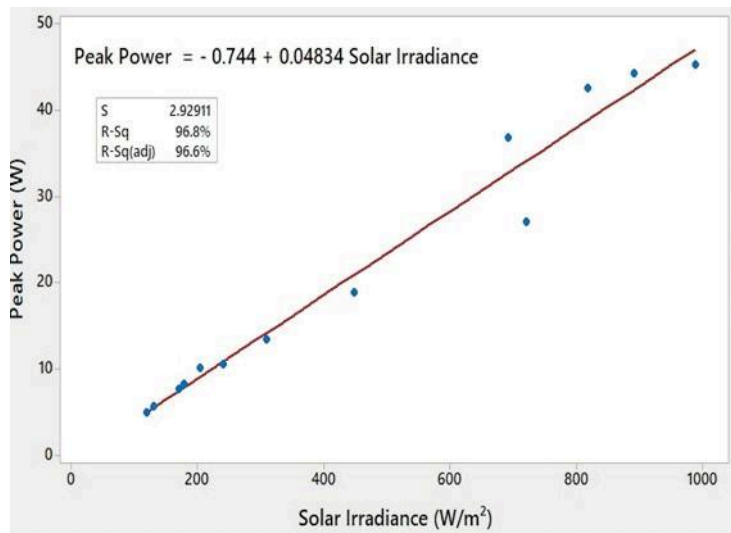

**Figure 6: Fitted regression line plot for Peak power versus Solar Irradiance (Day 5)**

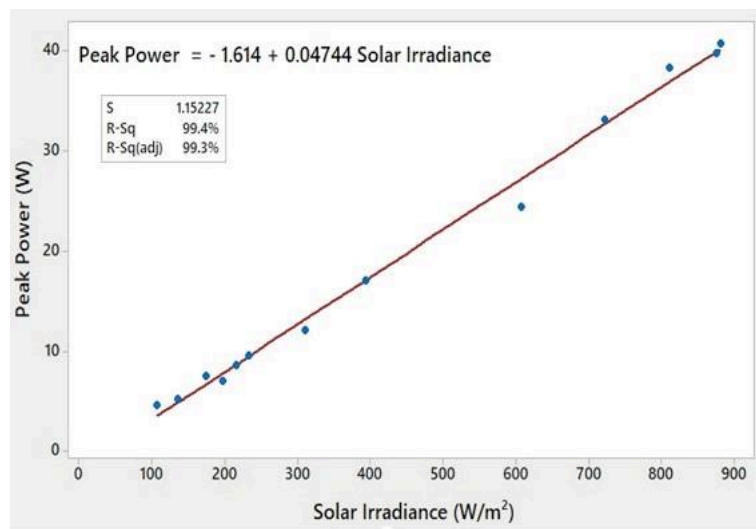

**Figure 7: Fitted regression line plot for Peak power versus Solar Irradiance (Day 8)**

Figure 8 to Figure 10 shows the fitted regression line plots of peak power vs relative humidity for days 1, 5 and 8 of the field experiments. The fitted regression line indicates that a negative correlation exists between the two quantities. The coefficient of determination, R<sup>2</sup> shows that the regression line fits the relationship to about 71.2%, 78.3% and 79.1% for days 1, 5 and 8 respectively. This can be attributed to the fact that high humidity causes reflection of solar irradiance in air thereby reducing the amount of irradiance reaching the panel and consequently reducing the performance. This agrees with the findings of (Amajama and Oku, 2016) who concluded that relative humidity has negative correlation with voltage, current and consequently on power output of solar panel.



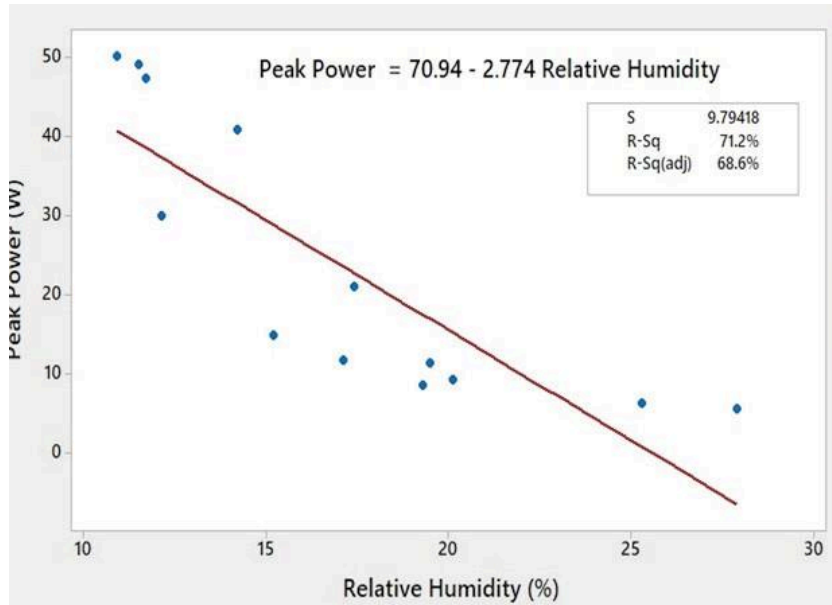


Figure 8: Fitted regression line plot for Peak power versus Relative Humidity (Day 1)


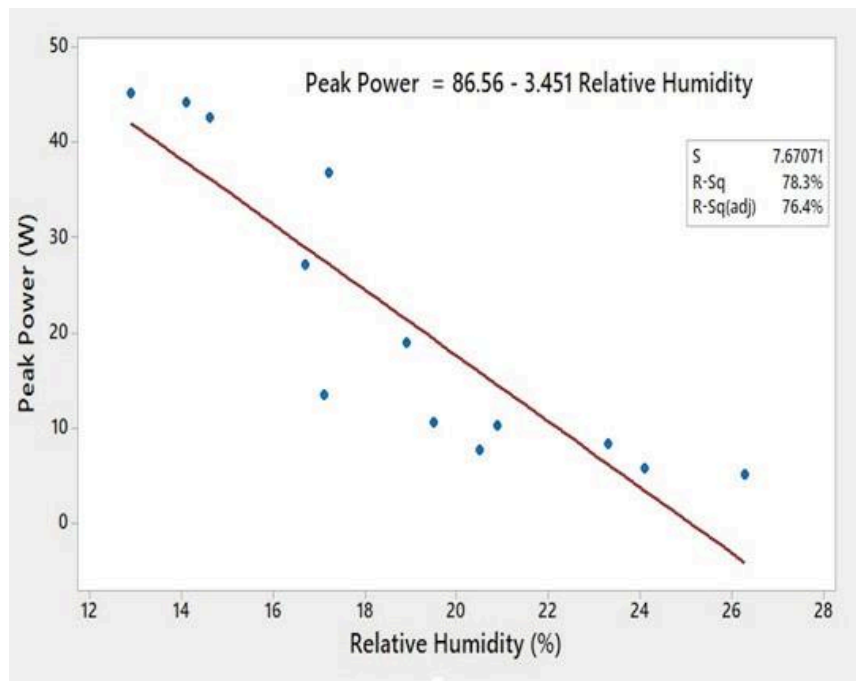



Figure 9: Fitted regression line plot for Peak power versus Relative Humidity (Day 5)

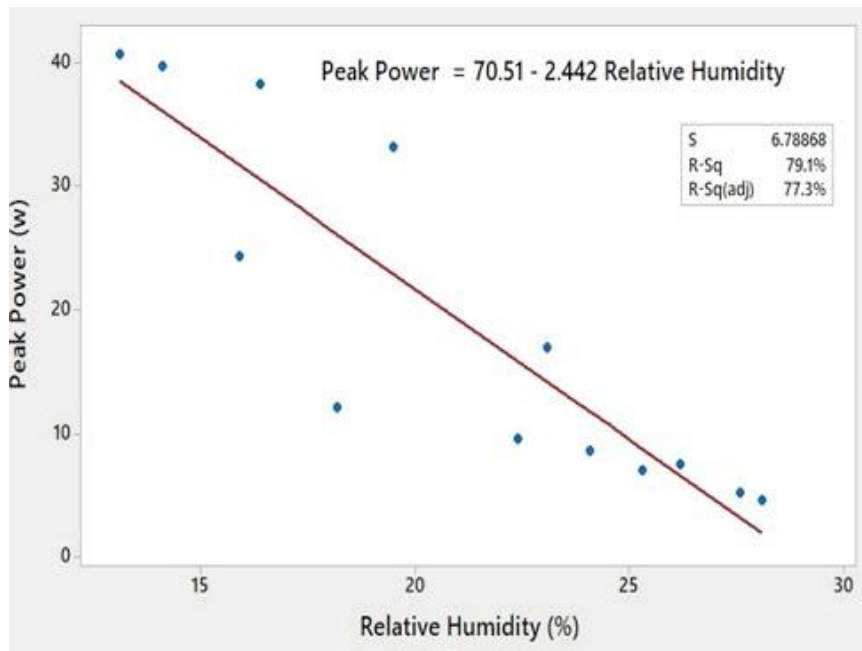

**Figure : Fitted regression line plot for Peak power versus Relative Humidity (Day 8)**

The coefficient of determination, R<sup>2</sup> shows that the regression line fits the relationship to about 71.2%, 78.3%, 79.1% and 72.4% for days 1, 5, 8 and 13 respectively. This can be attributed to the fact that high humidity causes reflection of solar irradiance in air thereby reducing the amount of irradiance reaching the panel and consequently reducing the performance. This agrees with the findings of (Amajama and Oku, 2016) who concluded that relative humidity has negative correlation with voltage, current and consequently on power output of solar panel.

**Figure 11** shows the particle sizes from each height of collection, panel and ground. The 0.5 m height contains larger particle size up to 1600 μm range. This is expected at lower heights. The highest height of 2.0 m contains the tiniest particle sizes and no larger particle beyond 516 μm. This is because finer particles tend to be blown higher than heavier ones.

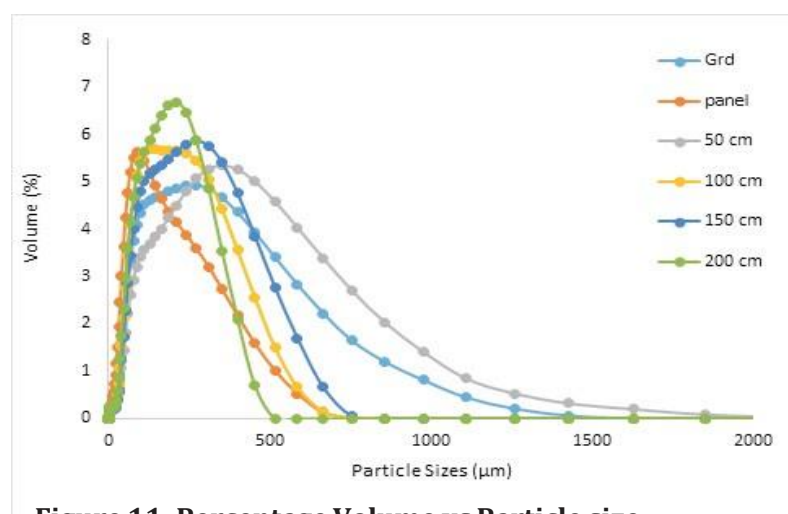

**Figure 11: Percentage Volume vs Particle size**

#### **4.0 Conclusion**

The impact of dust on the performance of solar PV system has not received the required global attention it deserves and only about 12% of global research reports is from Africa. This necessitated experimental investigation of impact of dust on solar PV modules in Maiduguri, North-Eastern Nigeria. The investigation which focused on the impact of continuous dust deposition on the modules revealed that the power output of a 50 W module which was used for the experimentation dropped by more than 50% and consequently the efficiency. This experiment was performed at the peak of dust event in Maiduguri and it can be concluded that dust deposition on solar PV module has tremendous impact on the overall performance of the system and cleaning of the modules at least once a week during this period will sustain the performance of the system. Sands were collected from the site of the field experiment in Maiduguri and subjected to chemical composition analysis, morphology, and size analysis. From the chemical composition and morphology of the sand collected from different heights during the field experiments, it can be concluded that the sand in the location of field experiments is quartz since the chemical analysis shows high percentage of oxygen and silicon. Its large particles which were found in the lower platform has higher roundness than those found at higher heights, therefore, deterioration or degradation rate of the PV module is expected to be low since rounder particles causes lower deterioration than particles with sharp edge.

#### **5.0 Recommendation**

The following recommendations were made based on the findings of this research:

- The development of solar PV system for energy supply to rural areas of the region under study is recommended as a result of huge availability of solar resource
- Cleaning of solar PV panel at least once a week is recommended for efficient performance of the system
- Further studies of dust impact is recommended to be carried out in other regions of Nigeria. This is because the result of dust impact from one region cannot be implied for other regions quantitatively.

#### **6.0 Acknowledgement**

The authors wish to thank the Petroleum Technology Development Fund (PTDF) Abuja for the sponsorship, Niger State College of Education, Minna for the Study Fellowship, Nigerian Meteorological Agency (NiMet) Abuja for data supply and Cranfield University, Cranfield, United Kingdom for the facilities.

## 7.0 References

- Amajama, J. and Oku, D. E. (2016). Effect of relative humidity on photovoltaic panels' output and solar illuminance/intensity, *Journal of Scientific & Engineering Research*, 3(4), pp. 126–130.
- Chanchangi, Y. N., Ghosh, A., Sundaram, S. and Mallick, T. K. (2020). Dust and PV performance in Nigeria: A review, *Renewable and Sustainable Energy Reviews*, 121(2020), pp. 1–14.
- Ibitoye , F. I. and Adenikinju, A. (2007). Future demand for electricity in Nigeria, *Applied Energy*, 84(5), pp. 492–504.
- Kamer, L. (2022) Population in Africa 2020, by country, [online] Available: <https://www.statista.com/statistics/1121246/population-in-africa-by-country/> (Accessed 22 March 2022).
- Karafil, A. Ozbay, H. and Kesler, M. (2016). Temperature and solar radiation effectson photovoltaic panel power," *Journal of New Results in Science*, 12(2016), pp. 48–58.
- Mann, P. E. (2012) 'Africa-EU Renewable Energy Cooperation Programme ( RECP ): What is the RECP ?', [online] Available: [https://www.climateinvestmentfunds.org/sites/cif\\_enc/files/RECP - Gender SREP Feb15.pdf](https://www.climateinvestmentfunds.org/sites/cif_enc/files/RECP - Gender SREP Feb15.pdf). (Accessed on 17 August 2019)
- Menoufi, K. (2017). Dust accumulation on the surface of photovoltaic panels: Introducing the Photovoltaic Soiling Index (PVSI)," *Sustainability.*, 9(6), pp. 963.
- Menoufi, K., Mohammed, H. F. M., Farghali,, A. A. and Khedr, M. H. (2017).Dust accumulation on photovoltaic panels: A case study at the East Bank of the Nile (Beni-Suef, Egypt)," *Energy Procedia*, 128, pp. 24–31.
- N. A. Nasiri, N. Patra, M. Pezoldt, J. Colas, and W. E. Lee, "Investigation of a single-layer EBC deposited on SiC/SiC CMCs: Processing and corrosion behaviour in high-temperature steam," *J. Eur. Ceram. Soc.*, vol. 39, no. 8, pp. 2703–2711, 2019